

ASX/Media Announcement

Perth: 24 November 2016

High Grade Lithium Drill Results at Lemare

- High-grade lithium confirmed by diamond drilling at Lemare
- Results include 21 m @ 2.65% Li₂O, 41.5 m @ 1.71% Li₂O and 23 m @ 1.61% Li₂O
- All lithium mineralisation contained within spodumene
- Main pegmatite extended to 300 m length, and open to the northeast
- New spodumene pegmatite identified to the SW, 600 m strike, up to 4.26% Li₂O in rock chip samples

Platypus Minerals Ltd ("Platypus" or "Company") is pleased to announce positive results from the Stage 1 exploration program recently completed at the Lemare Project.

The Lemare Project comprises 158 claims encompassing 74 km² in the Abitibi greenstone belt in the James Bay region of Quebec, Canada. Lemare is located approximately 60 km east of the town of Nemaska and sits 30 km east of the Whabouchi spodumene deposit owned by Nemaska Lithium (Figure 1).

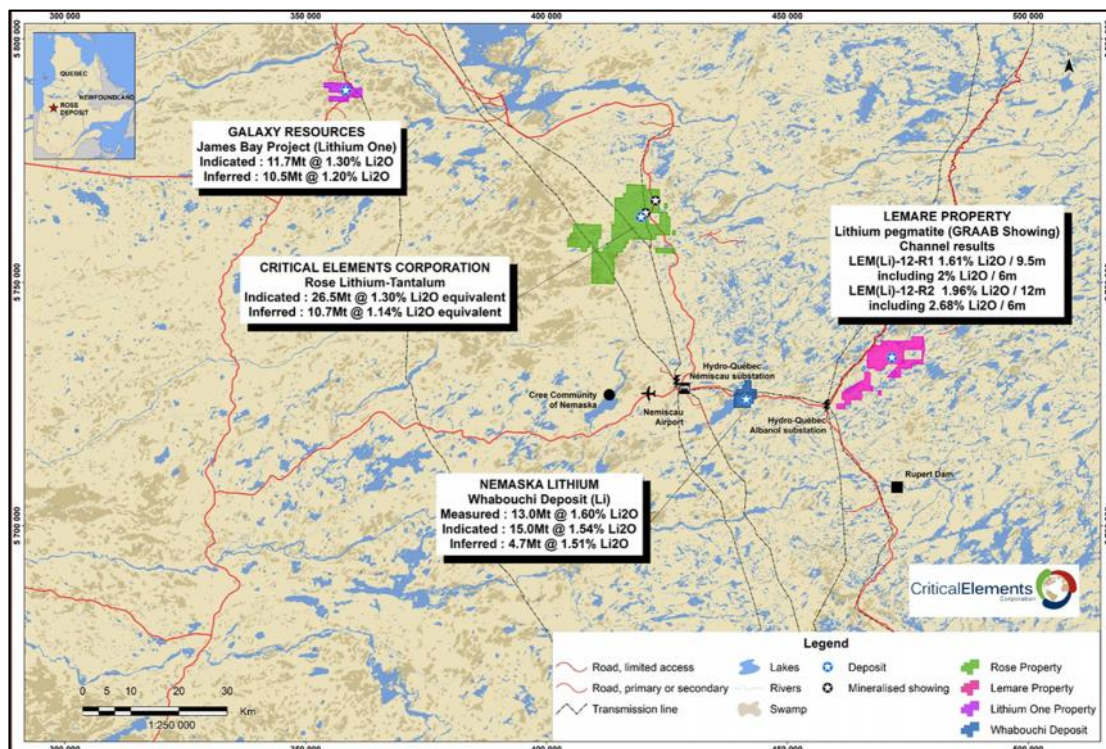


Figure 1. Location of the Lemare spodumene project in the James Bay region of Quebec, Canada, in relation to several advanced lithium projects.

The Company's first exploration program at Lemare comprised 16 diamond drill holes, totalling 1,788m of NQ core, drilled into the Lemare pegmatite along 8 lines spaced a nominal 50 m apart. In conjunction, a program of regional rock chip sampling was undertaken along the projected extension of the pegmatite beyond the bounding lake to the southwest (Figures 2 and 3).

The drilling confirmed the presence of a high grade spodumene pegmatite that was initially identified by a series of channel samples. This pegmatite is seen to extend at least 300 m along strike and remains open to the NE and down dip. It is up to 20 m in true width and pinches and swells both along strike and down dip (Figures 4 and 5). The pegmatite is closed off to the SW where it approaches a lake.

Several sub-parallel pegmatites were intersected by drilling. To date these have been generally low grade and only sporadically mineralised.

Better drill results include:

41.5 m @ 1.71% Li₂O, including 15 m @ 2.18% Li₂O and 3 m @ 3.6% Li₂O in hole LE-16-14;

21m @ 2.65% Li₂O in hole LE-16-13;

18.85 m @ 1.35% Li₂O, including 8.4 m @ 2.26 Li₂O in hole LE-16-07; and

23 m @ 1.61% Li₂O, including 10.5 m @ 2.51% Li₂O in hole LE-16-03.

Full details and results of the drilling are presented in Tables 1 and 2, below. A full set of assay results is included as Appendix 1.

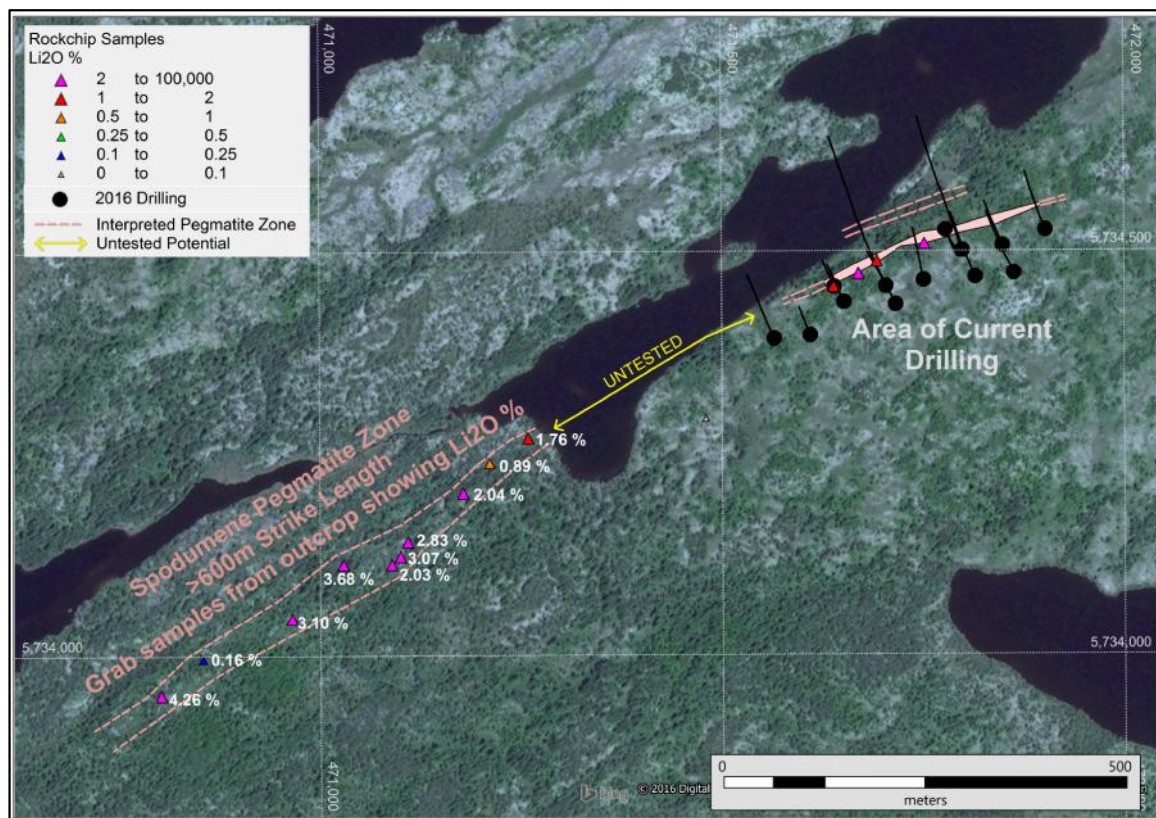


Figure 2. Stage 1 work program at Lemare, showing drilling into the known spodumene pegmatite and rock chip sampling of potential extensions to the southwest.

Rock chip sampling along the projected extension of the pegmatite beyond the lake to the SW has identified a new zone of spodumene mineralisation over a 600 m strike length (Figure 2). This zone remains open to the SW.

Fairly consistent grades of 2% - 3% Li_2O were recorded from intermittent pegmatite outcrops along a 600 m long strike (average of 10 samples is 2.3% Li_2O). This represents a newly identified mineralised zone that appears highly prospective and is therefore an attractive future drilling target.

The total Lemare spodumene-prospective pegmatite strike length now exceeds 1.2 km.

The new SW zone requires further prospecting, including trenching, and detailed mapping to determine the length and width of the pegmatite zone in order to target drilling in this area. The Company is considering the optimal exploration program during the winter season when the region is covered with snow.

Under the terms of the Lemare Option Agreement, the Company is earning up to a 75% interest in the project from owner Critical Elements Corporation (TSX-V:CRE). To maintain its position, the Company has an initial requirement to spend C\$800,000 on exploration by 31 March 2017 (extended from 31 December 2016 by mutual agreement with CRE) of which approximately C\$450,000 has been spent to date.

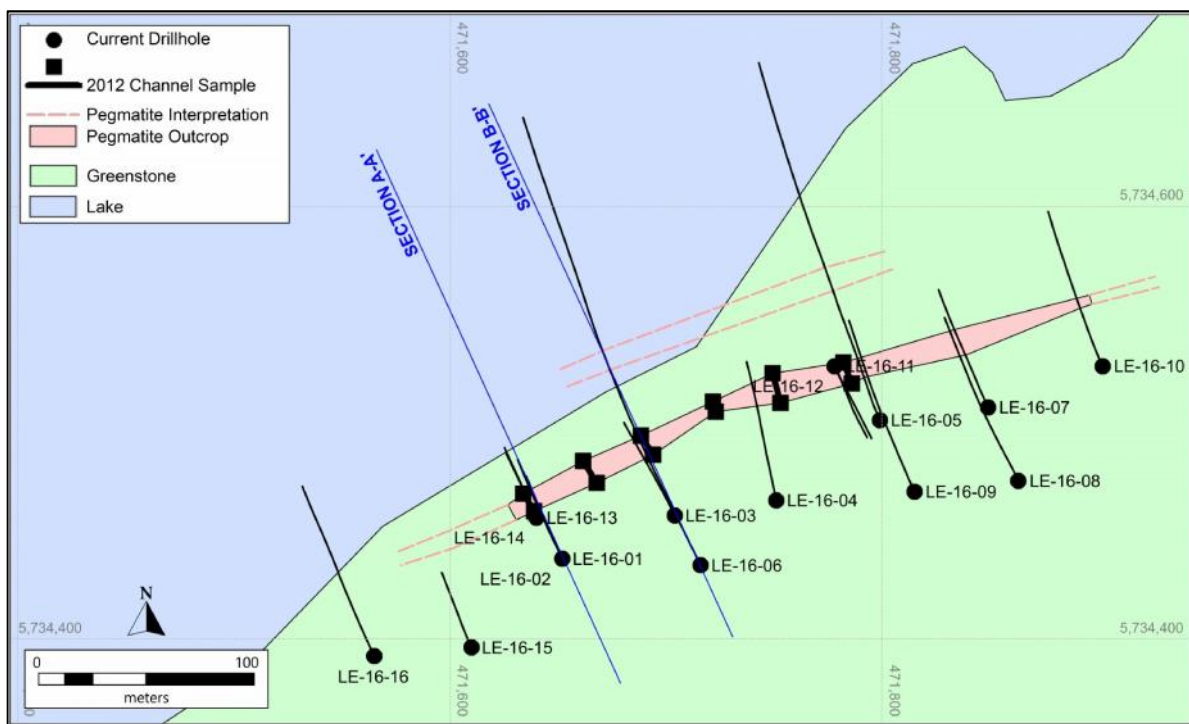


Figure 3. Drill hole location plan, Stage 1 diamond drilling at Lemare.

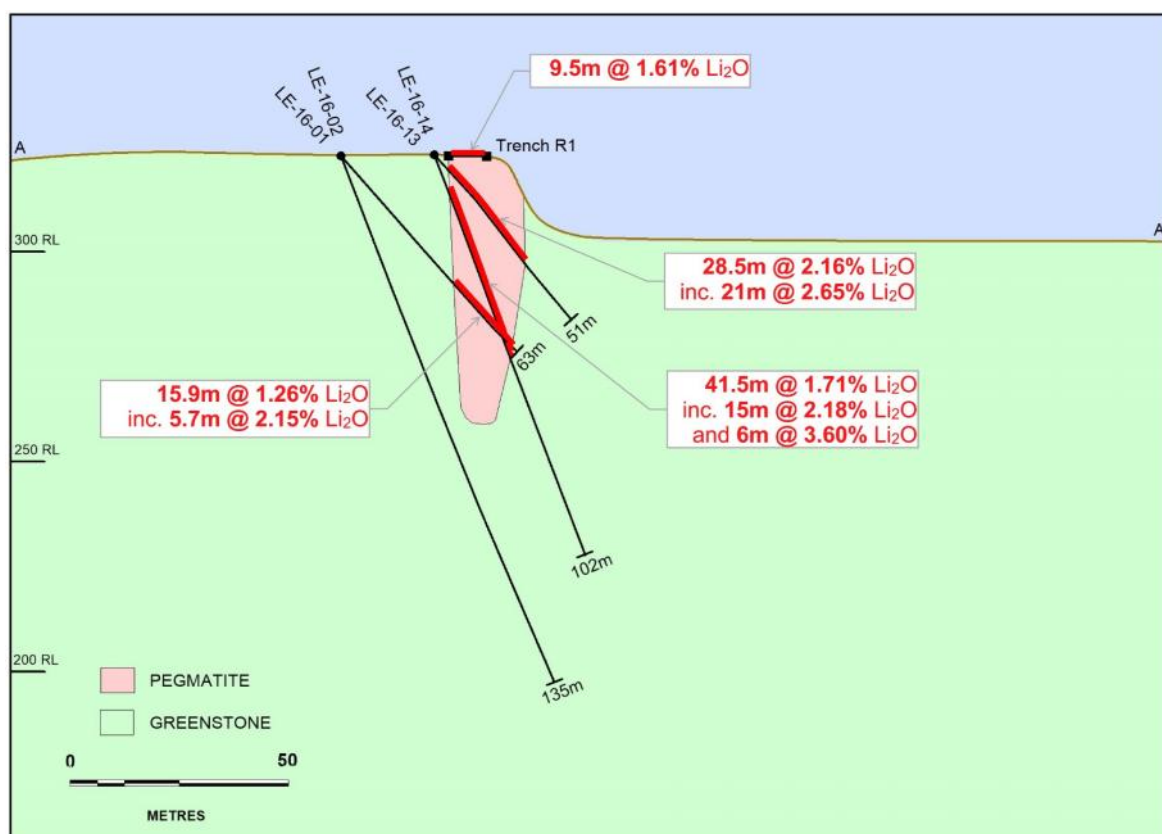


Figure 4. Lemare cross-section A-A' (Note: looking south).

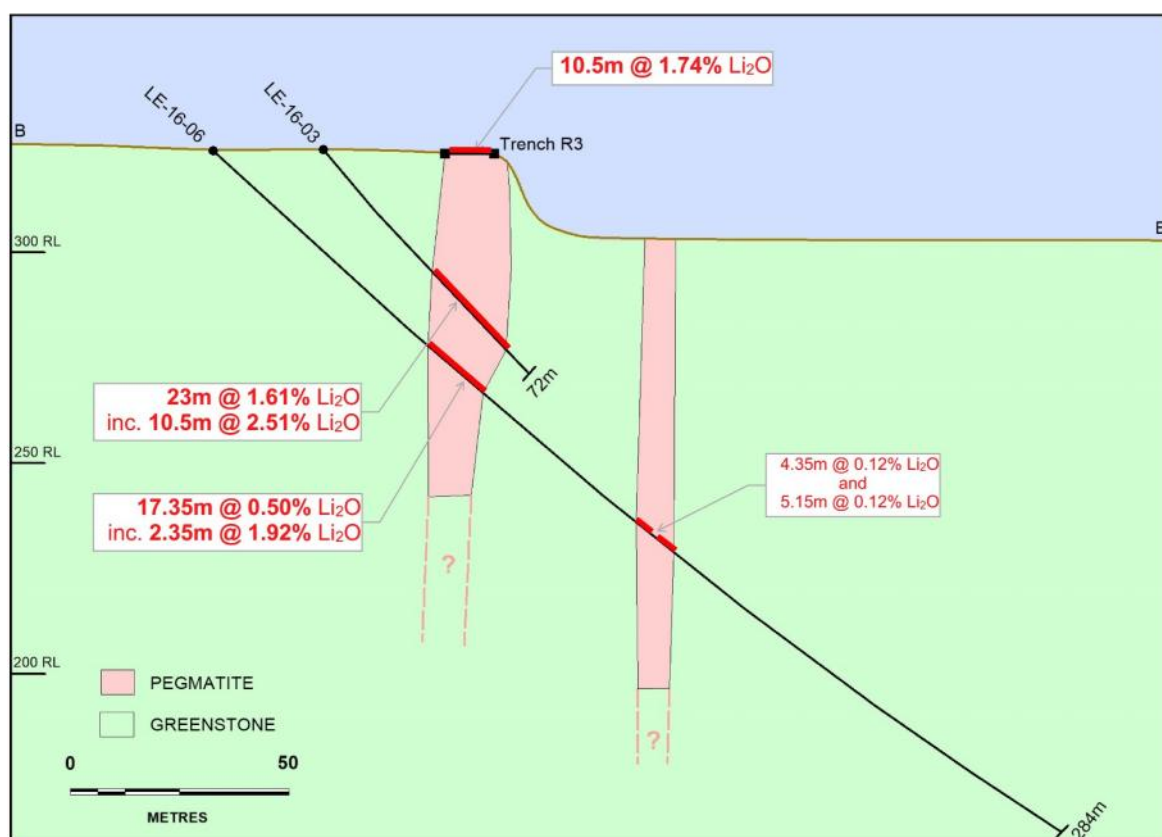


Figure 5. Lemare cross-section B-B' (Note: looking south).

Table 1. Results from the 16 diamond drill holes completed during the Stage 1 program at Lemare

Hole_ID	From (m)	To (m)	Down Hole Interval (m)	Li ₂ O (%)	True Width (m)
LE-16-01 incl	40.7	56.6	15.9	1.26	10.77
	45.2	50.9	5.7	2.15	3.86
LE-16-02	No Significant Result				
LE-16-03 incl	17.2	18.7	1.5	0.6	1
	25.9	31.6	5.7	0.21	3.8
	38.8	61.8	23	1.61	15.72
	44.8	55.3	10.5	2.51	7.18
LE-16-04	29.3	32.3	3	0.97	2.03
	47.9	51.9	4	1.25	2.81
	60.8	63.3	2.5	0.71	1.76
LE-16-05 incl	32.7	41.2	8.5	1.16	6.12
	35.2	40.5	5.3	1.79	3.82
	46	47.75	1.75	2.28	1.31
	86.3	100.5	12.2	0.08	9.26
LE-16-06 incl	68.5	85.85	17.35	0.5	13.13
	73.9	76.25	2.35	1.92	1.78
	132.9	137.25	4.35	0.12	3.39
	139.45	144.6	5.15	0.12	4.02
LE-16-07 incl	36	54.85	18.85	1.35	13.8
	39.6	48	8.4	2.26	6.15
LE-16-08	100.3	106.5	6.2	0.08	4.18
LE-16-09	81.85	85.85	4	0.72	2.72
	87.7	95.7	8	0.38	5.44
LE-16-10	40.2	47.1	6.9	0.17	4.98
	85.5	105	19.5	0.22	14.18
LE-16-11	8.8	23.65	14.85	0.25	9.77
	32.3	34.5	2.2	0.25	1.45
	44.8	46.8	2	0.1	1.32
LE-16-12 incl	14.45	32.9	18.45	0.87	6.37
	24.5	32.9	8.4	1.43	2.9
	55.5	62.5	5	0.12	1.77
	85	92.4	7.4	0.23	2.68
LE-16-13 incl	5.5	34	28.5	2.16	18.01
	7	28	21	2.65	13.27
LE-16-14 Incl And	10.5	52	41.5	1.71	14.26
	13.5	28.5	15	2.18	5.18
	42	48	6	3.6	2.06
LE-16-15	Missed Target				
LE-16-16	No Significant Result				

Overall intersections calculated on total width of pegmatite. Inclusive high grade zones calculated using 1% Li₂O cut with up to 1m of internal dilution.

Table 2. Lemare Diamond Drilling Collar Information

Hole_ID	Easting	Northing	RL	Depth (m)	AZIMUTH	DIP
LE-16-01	471652	5734437	323	63	335	-50
LE-16-02	471652	5734437	323	135	335	-70
LE-16-03	471704	5734457	324	72	335	-50
LE-16-04	471751	5734464	323	91	348	-46
LE-16-05	471799	5734501	329	225	335	-45
LE-16-06	471716	5734434	324	284	334	-43
LE-16-07	471849	5734507	329	81	335	-45
LE-16-08	471863	5734473	327	126	335	-50
LE-16-09	471815	5734468	327	126	335	-50
LE-16-10	471902	5734526	328	105	335	-45
LE-16-11	471778	5734526	319	57	155	-50
LE-16-12	471778	5734526	319	102	155	-70
LE-16-13	471640	5734456	323	51	335	-50
LE-16-14	471640	5734456	323	102	335	-70
LE-16-15	471610	5734396	320	51	335	-45
LE-16-16	471565	5734392	313	117	335	-45

Holes are NQ diamond and located in UTM NAD83 Zone 18 coordinates

Further Information

For further information, please contact

Joe Walsh
Managing Director
Platypus Minerals Ltd
 +61 (0) 417 928 590

Tom Dukovcic
Director Exploration
Platypus Minerals Ltd
 +61 (0)8 9363 7800

The information in this report that relates to Exploration Results is based on information compiled by Mr Tom Dukovcic, who is an employee of the Company and a member of the Australian Institute of Geoscientists and who has sufficient experience relevant to the styles of mineralisation and the types of deposit under consideration, and to the activity that has been undertaken, to qualify as a Competent Person as defined in the 2012 edition of the "Australasian Code for Reporting of Exploration Results, Mineral Resources and Ore Reserves." Mr Dukovcic consents to the inclusion in this report of information compiled by him in the form and context in which it appears.

About Platypus Minerals Ltd

Platypus Minerals Ltd is an ASX-listed Company focused on exploration, development and production of lithium. Its current exploration assets include options over the Lemare and the Royal projects, both in Quebec, Canada; ownership of the Euriowie project near Broken Hill in New South Wales; joint venture agreements with ASX-listed Crusader Resources (ASX:CAS) in Brazil and Latin Resources (ASX:LRS) in Peru and Argentina to jointly evaluate lithium opportunities. Through its wholly-owned subsidiary Lepidico Ltd, Platypus also owns the technology to a metallurgical process that has successfully produced lithium carbonate from non-conventional sources, specifically lithium-rich mica minerals including lepidolite and zinnwaldite. The L-Max® Process has the potential to disrupt the lithium market by providing additional lithium supply from alternative sources. On 27 September 2016 the Company announced the commencement of a pre-feasibility study for a Phase 1 L-Max® plant targeting production for 2019.

Appendix 1: Lemare Drilling Assay Data

Samples analysed at ALS Minerals Laboratory, Val D'or, Canada

Multi element analysis using 4 acid digest ICP-MS method ME-MS61, overlimit for Ta using Lithium Borate Fusion ICP-MS method ME-MS85, overlimit for Li using ore grade 4 acid digest ICP-AES method Li-OG63

	FROM	TO	SAMPLE_NO	Sample Type	AG_PPM	AL_PER	AS_PPM	BA_PPM	BE_PPM	BI_PPM	CA_PER	CS_PPM	FE_PER	GA_PPM	K_PER	LA_PPM	LI_PPM	MG_PER	MN_PPM	NA_PER	NB_PPM	P_PPM	RB_PPM	S_PER	SN_PPM	SR_PPM	TA_PPM	TI_PER	TL_PPM	W_PPM	Y_PPM	MS85_TA	LI-OG63
E-16-01	35.20	36.20	730651	BLANK	0.06	7.58	535.00	40.00	7.48	0.43	6.70	91.40	11.95	21.50	0.39	7.00	700.00	3.06	1800.00	1.45	5.60	840.00	115.50	0.26	28.30	97.90	2.61	0.98	0.87	1.20	35.10		
E-16-01	36.20	37.70	730652		0.13	7.65	32.60	-10.00	201.00	0.05	0.38	35.40	0.47	34.30	0.35	1.10	240.00	0.03	521.00	6.57	133.50	1890.00	110.00	0.01	26.90	21.30	>100.00	0.01	0.55	2.00	1.10	214.00	
E-16-01	37.70	39.20	730653		0.07	7.78	24.10	-10.00	236.00	0.10	0.39	38.80	0.56	30.50	0.35	0.70	570.00	0.07	959.00	6.73	178.00	2590.00	94.80	0.01	15.10	14.90	>100.00	0.02	0.44	1.30	1.00	196.00	
E-16-01	39.20	40.70	730654		0.09	6.81	24.00	-10.00	222.00	0.06	0.20	57.20	0.44	37.70	0.81	-0.50	470.00	0.02	625.00	5.31	127.50	1790.00	324.00	-0.01	61.10	12.50	100.00	0.01	1.44	1.80	0.20	104.50	
E-16-01	40.70	42.20	730655		0.06	7.21	22.60	-10.00	207.00	0.06	0.16	41.50	0.46	42.90	0.70	-0.50	5940.00	0.03	540.00	3.96	116.50	1200.00	237.00	-0.01	77.10	9.20	76.10	0.01	1.08	2.00	0.20		
E-16-01	42.20	43.70	730656		0.07	7.66	28.80	-10.00	176.00	0.07	0.22	34.70	0.57	41.80	0.60	-0.50	5840.00	0.03	765.00	4.69	113.00	1820.00	190.50	-0.01	51.70	12.10	99.90	0.01	0.89	1.90	0.10		
E-16-01	43.70	45.20	730657		0.04	6.73	28.80	-10.00	212.00	0.07	0.28	37.10	0.29	31.50	0.43	2.50	720.00	0.02	655.00	5.93	145.50	2260.00	141.50	0.01	27.50	15.60	>100.00	-0.01	0.68	1.60	1.50	179.00	
E-16-01	45.20	46.70	730658		0.05	6.75	12.50	-10.00	343.00	0.16	0.22	67.60	0.63	38.30	0.56	-0.50	6290.00	0.06	761.00	3.21	143.00	1840.00	217.00	-0.01	72.50	10.00	77.70	0.01	0.99	1.80	0.40		
E-16-01	46.70	48.20	730659		0.06	7.72	22.20	10.00	227.00	0.15	0.20	42.50	0.65	41.80	0.38	0.50	8380.00	0.13	648.00	3.72	110.00	1420.00	105.00	-0.01	57.00	10.50	100.00	0.01	0.52	1.40	0.70	100.00	
E-16-01	46.71	48.21	730660		0.08	8.09	1.90	550.00	0.71	0.12	4.60	0.74	4.28	15.20	1.14	10.00	12.60	1.58	981.00	2.44	3.00	730.00	14.70	-0.01	0.80	492.00	0.24	0.29	0.16	8.50	23.10		
E-16-01	48.20	49.70	730661	0.04	8.27	19.30	-10.00	210.00	0.54	0.10	58.60	0.73	55.80	0.59	-0.50	>10000.00	0.04	528.00	1.83	58.60	580.00	266.00	-0.01	112.50	6.20	50.40	0.01	1.24	1.30	0.20	1.40		
E-16-01	49.70	50.90	730662	0.01	6.91	14.50	-10.00	86.40	0.09	0.17	88.70	0.64	44.60	0.36	-0.50	>10000.00	0.06	412.00	1.82	46.80	530.00	198.50	-0.01	123.00	5.40	42.70	0.03	1.11	1.00	0.60		1.17	
E-16-01	50.90	52.30	730663	0.04	6.77	52.40	20.00	10.40	0.48	5.95	97.00	11.50	21.90	0.39	5.50	710.00	1.92	1680.00	1.02	7.10	1080.00	90.10	0.21	31.30	79.60	1.28	1.01	0.90	2.00	35.80			
E-16-01	52.30	53.70	730664	0.08	6.53	986.00	50.00	7.37	0.51	5.76	249.00	11.80	21.30	0.57	6.40	1100.00	1.98	1800.00	0.90	9.20	2230.00	295.00	0.39	43.10	75.00	1.92	1.06	2.26	35.10	37.00			
E-16-01	53.70	55.20	730665	0.05	7.41	2220.00	10.00	54.20	0.49	1.24	194.00	2.14	34.10	0.41	0.80	6110.00	0.30	616.00	3.24	68.20	1620.00	233.00	0.16	70.70	24.70	79.00	0.16	1.84	1.50	4.40			
E-16-01	55.20	56.60	730666	0.03	8.19	58.60	10.00	114.00	0.14	1.24	287.00	2.11	43.20	0.75	1.20	4180.00	0.32	549.00	3.86	75.70	1600.00	421.00	0.04	88.60	26.20	>100.00	0.17	2.62	2.50	5.50	121.00		
E-16-01	56.60	57.60	730667	0.12	6.54	13.70	20.00	13.90	0.46	5.43	415.00	10.90	22.00	0.53	6.70	830.00	1.86	1690.00	1.08	8.90	1430.00	317.00	0.18	49.00	69.50	31.70	0.96	2.40	30.30	35.80			
E-16-03	16.20	17.20	730668	0.05	7.35	5.30	50.00	1.70	0.22	6.00	126.00	10.20	18.30	0.43	5.30	1370.00	3.39	1540.00	1.55	3.30	540.00	154.00	0.01	6.40	135.50	0.43	0.74	1.09	0.30	28.60			
E-16-03	17.20	18.70	730669	0.03	7.13	8.20	10.00	221.00	0.09	0.67	76.60	1.01	39.80	0.54	0.90	2780.00	0.13	427.00	3.94	87.90	1660.00	240.00	-0.01	73.30	25.00	58.60	0.04	1.20	1.70	1.80			
E-16-03	18.70	19.90	730670	0.06	6.96	3.30	30.00	157.50	0.23	4.58	44.50	8.04	21.70	0.29	4.80	1210.00	2.16	1570.00	2.43	36.80	2400.00	70.00	0.06	18.00	92.90	22.10	0.61	0.48	0.60	23.40			
E-16-03	24.80	25.90	730671	0.03	6.66	6.10	80.00	10.80	0.23	4.63	257.00	10.25	20.00	0.85	5.80	1510.00	2.56	1600.00	1.74	7.00	750.00	339.00	0.02	42.90	124.00	6.80	0.79	2.43	0.60	29.40			
E-16-03	25.90	27.40	730672	0.04	7.63	10.60	20.00	130.50	0.08	0.68	32.70	0.84	33.40	0.27	2.30	1710.00	0.17	780.00	5.38	73.50	2540.00	71.20	0.01	24.60	32.70	76.40	0.03	0.42	0.80	2.10			
E-16-03	27.40	28.60	730673	0.14	5.71	4.60	90.00	4.11	0.29	6.25	108.00	9.87	15.20	0.70	10.00	950.00	4.95	1720.00	1.08	9.00	550.00	224.00	0.04	16.60	101.00	1.61	0.69	1.35	0.90	26.50			
E-16-03	28.60	30.10	730674	0.03	7.08	7.50	20.00	189.00	0.10	0.75	43.20	1.00	52.00	1.35	0.80	560.00	0.17	1410.00	3.42	95.30	4590.00	470.00	-0.01	172.00	33.40	31.90	0.03	1.77	4.20	2.20			
E-16-03	30.10	31.60	730675	0.10	7.16	14.10	40.00	186.50	0.24	2.97	452.00	5.25	36.80	0.99	3.50	750.00	2.03	1880.00	2.86	67.60	6460.00	510.00	0.12	75.40	118.00	38.90	0.33	3.37	2.10	12.30			
E-16-03	31.60	33.10	730676	0.05	7.50	3.10	40.00	6.03	0.21	6.10	26.70	9.94	19.50	0.21	6.30	361.00	2.90	1420.00	1.96	4.60	810.00	42.60	0.26	8.40	167.50	1.10	0.78	0.23	5.00	30.50			
E-16-03	31.61	33.11	730677	BLANK	0.06	8.11	0.80	550.00	0.69	0.14	4.60	0.69	4.27	15.40	1.16	10.70	6.30	1.61	1020.00	2.47	3.10	740.00	14.90	-0.01	0.80	479.00	0.22	0.30	0.17	8.80	23.50		
E-16-03	33.10	34.60	730678		0.07	7.07	4.10	30.00	3.03	0.17	5.29	17.10	10.45	18.35	0.12	6.30	610.00	3.30	1420.00	2.48	4.20	900.00	15.50	0.83	4.20	100.50	0.69	0.83	0.12	0.90	31.60		
E-16-03	34.60	36.10	730679		0.08	7.01	3.40	40.00	0.82	0.19	4.97	26.90	11.00	18.85	0.12	6.70	500.00	3.22	1480.00	2.56	4.10	970.00	12.50	1.32	1.30	87.90	0.31	0.87	0.16	2.50	33.00		
E-16-03	36.10	37.60	730680		0.05	6.66	2.90	60.00	0.78	0.12	4.48	136.50	10.95	19.10	0.22	8.20	770.00	2.93	1510.00	2.21	4.80	970.00	43.00	0.95	1.30	109.50	0.37	0.94	0.29	1.30	38.00		
E-16-03	37.60	38.80	730681	0.15	6.91	4.50	100.00	1.68	0.24	4.90	75.40	10.45	19.80	0.61	7.80	1280.00	2.55	1420.00	1.61	4.60	960.00	165.50	1.14	8.40	208.00	0.56	0.90	0.88	1.10	37.50			
E-16-03	38.80	40.30	730682	0.03	8.25	27.00	-10.00	242.00	0.10	0.35	28.90	0.79	41.10	0.24	-0.50	7850.00	0.05	757.00	4.60	89.90	1510.00	55.00	0.02	30.60	15.35								

LE-16-04	63.30	64.30	730714		0.05	6.84	5.50	70.00	4.68	0.34	5.72	32.10	12.25	20.40	0.36	5.40	1380.00	2.46	1800.00	1.39	5.30	810.00	65.40	0.23	11.60	125.50	3.91	1.05	0.49	0.70	31.10		
LE-16-05	32.70	33.90	730715		0.04	4.63	14.20	-10.00	252.00	0.11	0.49	32.50	0.90	18.10	0.19	0.70	480.00	0.06	1550.00	3.42	55.80	4110.00	55.90	0.01	7.90	25.80	28.20	0.02	0.32	0.90	1.10		
LE-16-05	33.90	35.20	730716		0.04	5.50	9.40	10.00	272.00	0.15	0.47	43.40	0.92	39.20	1.34	0.60	690.00	0.06	1240.00	2.24	102.00	4190.00	440.00	-0.01	133.50	26.40	31.00	0.02	2.00	3.70	1.00		
LE-16-05	33.91	35.21	730717	DUPLICATE	-0.01	6.08	8.50	10.00	194.00	0.11	0.49	40.60	0.92	41.80	1.40	0.60	1960.00	0.06	1340.00	2.37	88.00	4480.00	440.00	-0.01	131.50	28.60	26.60	0.02	2.01	4.00	1.10		
LE-16-05	35.20	36.00	730718		0.03	6.39	11.40	10.00	223.00	0.09	0.34	46.90	0.98	50.10	1.50	-0.50	5430.00	0.06	1090.00	1.47	75.40	2710.00	480.00	-0.01	149.50	14.50	15.30	0.02	2.23	3.90	0.90		
LE-16-05	36.00	37.50	730719		0.01	6.96	13.00	20.00	277.00	0.10	0.43	59.40	1.11	54.30	1.26	-0.50	9730.00	0.07	1560.00	1.37	91.00	3900.00	411.00	-0.01	124.50	16.50	23.70	0.02	2.00	3.70	1.00		
LE-16-05	37.50	39.00	730720		0.05	7.41	16.80	10.00	320.00	0.12	0.31	79.00	0.84	47.20	0.70	-0.50	9970.00	0.04	1040.00	2.43	231.00	2390.00	234.00	-0.01	75.50	15.70	91.80	0.01	1.09	3.00	0.70		
LE-16-05	39.00	40.50	730721		0.04	6.92	5.60	-10.00	288.00	0.12	0.21	43.50	0.59	41.50	0.46	-0.50	6780.00	0.02	651.00	3.68	144.50	1310.00	162.00	-0.01	77.50	10.40	73.20	0.01	0.69	1.80	0.70		
LE-16-05	40.50	41.20	730722		0.02	7.83	21.10	-10.00	261.00	0.06	0.51	18.55	0.48	37.10	0.15	1.10	210.00	0.01	536.00	7.16	168.00	2450.00	28.20	0.01	13.20	35.90	>100.00	-0.01	0.13	1.60	1.30	232.00	
LE-16-05	46.00	47.75	730723		0.57	8.17	16.10	10.00	133.50	4.25	0.34	121.00	1.12	53.10	0.79	-0.50	>10000.00	0.08	881.00	2.84	81.90	1480.00	351.00	0.01	92.70	15.20	78.10	0.04	1.89	2.60	1.40		1.06
LE-16-05	86.30	87.50	730724		0.04	5.73	6.80	20.00	431.00	0.20	0.34	118.00	1.25	23.90	2.05	0.60	470.00	0.12	682.00	2.82	58.20	1230.00	840.00	0.02	44.40	14.00	62.80	0.06	5.11	1.40	2.00		
LE-16-05	87.50	89.00	730725		0.03	5.79	9.40	10.00	117.50	0.16	0.33	124.50	0.83	26.40	3.77	4.70	241.00	0.06	1720.00	1.63	144.00	2820.00	1410.00	0.01	72.30	23.70	>100.00	0.01	8.95	2.70	0.50	107.50	
LE-16-05	87.51	89.01	730726	BLANK	0.07	7.90	1.90	550.00	1.06	0.12	4.54	0.88	4.30	16.15	1.16	10.70	12.20	1.58	1020.00	2.48	3.30	740.00	18.60	-0.01	1.00	495.00	0.55	0.31	0.18	8.80	24.70		
LE-16-05	89.00	90.00	730727		0.06	5.34	5.40	10.00	306.00	0.05	0.30	126.00	1.26	30.80	3.45	1.00	510.00	0.08	3110.00	0.91	119.50	3770.00	1170.00	-0.01	138.50	16.70	85.10	0.02	7.04	3.40	0.20		
LE-16-05	90.00	91.00	730728		0.05	5.31	8.40	10.00	210.00	0.04	0.23	112.50	1.27	33.60	3.15	0.90	1210.00	0.09	2940.00	0.98	34.70	6930.00	1100.00	0.01	148.00	15.40	11.40	0.01	6.38	2.50	0.20		
LE-16-05	92.00	93.00	730729		0.01	6.52	12.50	10.00	229.00	0.08	0.19	59.60	0.47	35.10	1.57	0.80	132.50	0.03	253.00	4.26	57.60	1240.00	540.00	-0.01	80.20	13.20	31.80	0.01	3.09	2.10	0.50		
LE-16-05	94.00	95.00	730730		0.41	8.74	14.70	10.00	535.00	0.11	0.73	111.00	1.44	56.60	2.14	8.00	450.00	0.12	1670.00	3.95	95.80	4920.00	760.00	0.04	195.50	32.60	45.70	0.02	3.74	5.30	1.20		
LE-16-05	95.00	96.00	730731		0.03	6.49	4.40	10.00	69.20	1.94	0.87	57.40	0.90	43.70	1.92	6.20	379.00	0.07	992.00	2.70	126.00	5660.00	620.00	0.01	152.00	36.50	58.60	0.01	2.95	4.50	1.00		
LE-16-05	96.00	97.50	730732		0.04	7.74	14.20	10.00	163.00	4.79	0.55	65.10	0.59	42.80	1.55	0.70	147.50	0.04	468.00	4.94	52.40	3130.00	480.00	0.01	104.50	20.40	30.20	0.01	2.35	2.50	1.00		
LE-16-05	97.50	99.00	730733		0.02	7.70	13.60	10.00	249.00	0.31	0.52	86.90	0.65	38.50	2.14	0.60	242.00	0.05	630.00	4.52	62.20	3680.00	670.00	0.02	85.40	24.30	30.80	0.01	3.51	2.20	0.40		
LE-16-05	99.00	100.50	730734		0.04	7.29	8.10	-10.00	221.00	2.23	0.41	46.10	0.52	34.20	0.90	1.40	141.50	0.05	592.00	5.48	71.20	2430.00	285.00	0.01	49.50	19.10	66.10	0.01	1.42	1.40	0.40		
LE-16-05	55.60	55.90	730735		0.02	7.23	4.30	30.00	130.00	0.04	1.55	234.00	2.45	37.50	0.93	1.50	720.00	0.64	800.00	3.84	75.40	3200.00	520.00	0.02	48.10	45.70	41.70	0.17	4.06	1.00	5.60		
LE-16-05	55.61	55.91	730736	DUPLICATE	0.01	7.39	5.10	30.00	167.50	0.05	1.48	184.50	1.92	39.50	0.77	1.40	520.00	0.47	884.00	4.33	78.70	3610.00	412.00	0.01	44.50	40.20	44.00	0.12	3.15	1.00	3.90		
LE-16-05	56.40	56.75	730737		0.03	7.88	16.80	80.00	294.00	0.05	2.01	200.00	2.71	47.30	0.73	1.50	448.00	0.53	2870.00	4.16	85.70	2860.00	367.00	0.04	42.30	72.80	30.90	0.15	2.70	0.80	8.70		
LE-16-05	59.15	60.25	730738		-0.02	6.28	7.70	30.00	358.00	0.03	0.92	81.20	1.64	25.50	0.31	0.90	204.00	0.28	2010.00	4.02	61.20	1870.00	123.50	0.04	13.00	56.10	39.70	0.07	0.81	0.60	2.80		
LE-16-05	67.95	68.25	730739		-0.01	7.44	21.20	10.00	108.00	0.05	1.71	81.10	0.86	31.10	0.25	0.70	217.00	0.17	219.00	5.34	62.80	3570.00	102.00	0.05	22.90	59.10	>100.00	0.05	0.85	1.20	4.50	193.00	
LE-16-05	68.25	68.50	730740		0.13	7.05	4.50	70.00	19.20	0.21	3.46	>500.00	8.86	19.85	1.59	3.60	1560.00	2.70	1860.00	1.31	4.10	680.00	950.00	0.73	197.00	59.10	1.22	0.63	7.38	1.00	27.80		
LE-16-05	68.50	69.35	730741		-0.01	7.79	14.90	10.00	180.50	0.07	0.55	24.40	0.45	38.80	0.23	0.80	233.00	0.04	752.00	6.71	172.50	2510.00	46.40	0.01	14.00	23.60	>100.00	0.01	0.26	1.80	1.70	185.00	
LE-16-05	69.35	69.60	730742		0.05	7.29	6.20	120.00	27.00	0.31	3.21	>500.00	8.85	27.80	2.66	3.60	2080.00	2.83	1880.00	0.83	13.30	1020.00	1750.00	0.13	157.50	52.80	8.88	0.68	14.30	27.30	23.70		
LE-16-05	69.60	71.00	730743		-0.02	7.35	7.80	-10.00	176.00	0.04	0.38	36.00	0.52	40.70	0.39	0.90	1560.00	0.06	806.00	5.65	143.50	2100.00	116.50	-0.01	34.30	19.10	>100.00	0.01	0.60	1.50	1.10	187.50	
LE-16-05	71.00	72.50	730744		0.02	7.24	16.40	-10.00	239.00	0.05	0.23	32.30	0.48	36.60	0.37	-0.50	65.00	0.03	705.00	6.22	125.00	1860.00	92.20	-0.01	18.80	18.40	99.50	-0.01	0.42	1.60	0.40		
LE-16-05	72.50	73.90	730745		-0.01	6.83	20.40	-10.00	174.50	0.05	0.17	53.90	0.52	47.80	0.77	-0.50	3450.00	0.05	652.00	3.86	104.00	1630.00	311.00	-0.01	81.30	14.00	58.50	0.01	1.61	2.20	0.10		
LE-16-05	72.51	73.91	730746	BLANK	0.08	8.29	1.60	540.00	0.93	0.12	4.55	0.90	4.22	17.40	1.17	13.80	10.90	1.59	1000.00	2.42	3.40	730.00	23.40	-0.01	1.10	488.00	0.42	0.29	0.20	8.90	26.90		
LE-16-05	73.90	75.10	730747		0.01	8.34	20.10	10.00	176.50	0.18	0.15	46.70	0.76	57.40	0.57	-0.50	>10000.00	0.11	722.00	2.83	90.10	720.00	177.00	-0.01	78.60	13.00	42.10	0.01	0.89	1.80	0.30		1.24
LE-16-05	75.10	76.25	730748		0.03	6.30	25.60	-10.00	272.00	0.20	0.19	54.00	0.55	36.80	0.41	0.50	5250.00	0.06	736.00	3.33	172.00	1840.00	132.00	-0.01	56.30	15.70	>100.00	0.01	0.65	1.80	0.60	133.00	
LE-16-05	76.25	77.20	730749		0.01	7.43	23.20	-10.00	171.50	0.05	0.26	38.60	0.54	42.20	0.56	0.50	1510.00	0.06	658.00	5.55	117.00	1700.00	175.00	-0.01	42.00	20.20	>100.00	0.01	0.86	1.80	0.50	141.00	
LE-16-05	77.20	78.35	730750		-0.02	7.26	16.50	-10.00	273.00	0.05	0.29	45.50	0.43	40.40	0.48	1.00	750.00	0.03	866.00	6.32	128.00	2580.00	157.50	0.01	32.40	19.50	>100.00	-0.01	0.79	1.40	0.60	188.50	
LE-16-05	78.35	79.05	730751		-0.01	6.88	19.80	-10.00	225.00	0.06	0.22	38.60	0.43	37.60	0.31	-0.50	3560.00	0.03	465.00	5.11	183.00	1530.00	68.70	-0.01	30.90	20.60	>100.00	-0.01	0.38	1.50	0.70	161.00	
LE-16-05	79.05	80.10																															

LE-16-07	38.20	39.60	730786		0.09	6.86	14.40	120.00	11.90	0.46	4.96	446.00	11.30	24.10	1.29	7.00	1340.00	1.89	2420.00	0.97	15.40	1450.00	760.00	0.08	74.60	96.50	36.70	0.98	5.45	1.20	35.90		
LE-16-07	39.60	40.85	730787		0.03	7.50	11.10	10.00	130.50	0.08	0.50	51.30	1.04	50.10	1.59	-0.50	5560.00	0.07	1180.00	2.50	81.60	2890.00	500.00	-0.01	136.50	16.70	26.80	0.03	2.41	3.50	1.60		
LE-16-07	40.85	42.00	730788		0.07	7.14	14.80	10.00	159.00	0.12	0.34	37.00	1.04	50.30	1.11	-0.50	>10000.00	0.05	1220.00	1.25	67.50	2750.00	352.00	-0.01	106.50	11.00	18.00	0.02	1.70	2.70	1.30	1.18	
LE-16-07	42.00	43.00	730789		0.03	6.94	5.10	20.00	154.50	0.08	0.20	52.80	0.90	51.20	2.04	-0.50	3590.00	0.07	660.00	2.08	113.00	1590.00	620.00	-0.01	169.50	12.00	29.90	0.03	2.90	4.90	0.50		
LE-16-07	43.00	44.30	730790		0.03	7.37	13.30	10.00	138.00	0.35	0.09	37.10	0.86	50.20	0.66	-0.50	>10000.00	0.03	804.00	1.11	78.10	850.00	228.00	-0.01	115.00	7.50	30.60	0.01	1.04	2.10	0.10	1.45	
LE-16-07	44.30	45.00	730791		0.06	6.92	10.80	-10.00	152.00	0.21	0.29	30.60	0.64	33.30	0.42	-0.50	4670.00	0.02	652.00	4.45	123.00	1910.00	126.00	-0.01	49.60	14.60	55.00	-0.01	0.58	1.70	0.80		
LE-16-07	45.00	46.50	730792		0.03	7.45	12.60	-10.00	149.50	0.24	0.09	30.20	0.70	46.30	0.28	-0.50	>10000.00	0.02	912.00	1.60	65.50	720.00	93.10	-0.01	113.50	6.10	34.00	0.01	0.41	0.90	0.10	1.54	
LE-16-07	46.50	48.00	730793		0.03	7.36	11.10	10.00	200.00	0.11	0.14	40.40	0.66	45.90	0.50	-0.50	>10000.00	0.02	684.00	1.97	87.80	940.00	178.50	-0.01	108.00	8.10	39.20	0.01	0.75	1.50	0.40	1.26	
LE-16-07	46.51	48.01	730794	DUPLICATE	-0.01	7.19	9.00	10.00	129.50	0.20	0.17	35.50	0.77	46.10	0.50	-0.50	>10000.00	0.02	778.00	1.81	83.00	1120.00	178.00	-0.01	117.50	8.50	35.50	0.01	0.78	1.50	0.40	1.25	
LE-16-07	48.00	49.50	730795		-0.01	6.46	4.50	60.00	105.50	0.13	0.34	83.90	0.93	50.60	3.06	-0.50	2690.00	0.09	621.00	0.98	80.70	2050.00	970.00	-0.01	167.50	21.90	11.75	0.03	4.65	5.00	0.70		
LE-16-07	49.50	51.00	730796		0.04	6.43	11.10	20.00	331.00	0.22	0.25	64.80	0.95	45.00	1.73	-0.50	5560.00	0.05	1040.00	1.67	81.30	2230.00	520.00	-0.01	115.50	12.00	21.40	0.02	2.60	3.10	0.60		
LE-16-07	51.00	52.50	730797		0.04	6.35	18.80	-10.00	180.00	0.14	0.27	37.90	0.55	37.40	0.72	-0.50	2020.00	0.02	1050.00	3.92	106.50	1580.00	230.00	-0.01	68.30	13.20	38.10	0.01	1.09	1.90	0.70		
LE-16-07	52.50	53.70	730798		0.03	6.73	34.00	10.00	190.00	0.19	0.23	48.90	0.55	39.70	1.00	-0.50	1760.00	0.02	905.00	4.61	105.50	1810.00	279.00	-0.01	65.00	15.40	56.80	-0.01	1.66	1.50	0.60		
LE-16-07	53.70	54.85	730799		-0.01	6.60	29.20	-10.00	189.50	0.10	0.36	32.10	0.47	34.90	0.40	0.80	259.00	0.12	643.00	5.08	140.50	1910.00	134.00	-0.01	36.80	30.20	>100.00	0.01	0.67	1.70	0.90	128.50	
LE-16-08	100.30	102.00	730800		-0.01	7.96	10.20	30.00	202.00	0.03	0.80	41.90	0.92	41.80	2.66	0.70	365.00	0.12	1040.00	3.74	61.40	3730.00	650.00	0.01	118.00	81.80	14.90	0.02	3.25	3.10	1.20		
LE-16-08	102.00	103.50	730801		-0.01	6.49	19.70	20.00	235.00	0.19	0.57	36.30	0.71	41.80	1.85	0.70	356.00	0.06	1220.00	3.02	104.50	3870.00	510.00	-0.01	151.50	18.70	29.20	0.02	2.32	3.70	1.40		
LE-16-08	103.50	105.00	730802		-0.01	6.06	23.00	10.00	226.00	0.17	0.44	37.80	0.86	42.70	1.48	-0.50	580.00	0.07	1400.00	2.46	122.50	4140.00	470.00	-0.01	185.50	17.70	34.00	0.02	2.03	4.40	0.70		
LE-16-08	105.00	106.50	730803		-0.01	6.88	12.60	10.00	169.00	0.16	0.36	23.60	0.49	34.70	0.72	-0.50	278.00	0.03	768.00	5.19	150.50	2410.00	201.00	-0.01	77.30	16.90	94.10	0.01	0.85	2.30	0.80		
LE-16-09	81.85	83.35	730804		0.08	6.81	10.30	-10.00	146.50	0.08	0.40	19.05	0.55	34.20	0.54	10.10	1080.00	0.10	655.00	5.02	103.50	2050.00	152.00	0.01	55.70	24.00	48.10	0.01	0.64	2.20	1.70		
LE-16-09	83.35	84.55	730805		0.04	6.07	7.20	10.00	268.00	0.08	0.35	36.40	0.74	39.30	1.05	2.90	2350.00	0.09	638.00	2.89	90.20	2050.00	339.00	-0.01	103.00	19.70	26.90	0.01	1.45	3.30	1.20		
LE-16-09	84.55	85.85	730806		0.08	7.51	12.40	-10.00	124.50	0.66	0.33	16.00	0.66	41.50	0.40	-0.50	6830.00	0.05	855.00	4.17	78.10	2010.00	106.50	-0.01	40.90	16.60	32.80	0.01	0.46	1.70	0.50		
LE-16-09	87.70	88.50	730807		-0.01	7.83	7.20	10.00	294.00	0.15	0.86	47.20	1.42	42.40	1.30	1.00	1180.00	0.14	2230.00	5.12	71.30	6690.00	348.00	0.01	93.20	34.10	33.10	0.05	1.89	2.00	2.30		
LE-16-09	87.71	88.51	730808	BLANK	0.09	7.70	1.10	540.00	0.73	0.12	4.52	0.78	4.23	15.95	1.15	11.20	6.30	1.55	996.00	2.46	3.10	720.00	14.50	-0.01	0.80	480.00	0.23	0.29	0.18	8.60	24.20		
LE-16-09	88.50	88.85	730809		0.07	6.77	14.60	70.00	57.10	0.39	3.61	150.00	8.51	29.50	1.41	5.30	1000.00	1.34	29.10	3430.00	412.00	0.12	115.50	52.50	14.75	0.70	3.12	6.10	1.62	26.40			
LE-16-09	88.85	90.00	730810		0.01	6.97	8.50	20.00	202.00	0.11	1.04	52.30	1.50	34.40	1.33	1.30	780.00	0.19	1960.00	4.26	115.00	6170.00	332.00	-0.01	64.10	27.80	85.30	0.08	1.94	2.60	4.20		
LE-16-09	90.00	91.25	730811		0.02	6.59	6.50	10.00	169.00	0.06	0.41	22.40	0.57	42.70	1.11	-0.50	274.00	0.04	512.00	4.54	103.00	2290.00	285.00	-0.01	98.70	22.30	39.50	0.01	1.23	3.10	1.10		
LE-16-09	91.25	92.85	730812		0.04	6.36	5.60	-10.00	118.50	0.08	0.21	18.85	0.67	41.50	0.69	-0.50	6620.00	0.04	660.00	2.88	48.60	1250.00	180.50	-0.01	62.50	10.70	15.55	0.01	0.83	1.70	0.40		
LE-16-09	92.85	93.50	730813		0.02	6.33	11.30	-10.00	351.00	0.39	0.65	34.10	0.99	37.90	0.91	3.40	560.00	0.06	2670.00	4.04	94.30	5640.00	252.00	-0.01	83.30	28.80	29.60	0.01	1.14	2.90	2.90		
LE-16-09	93.50	94.75	730814		0.01	6.33	8.50	-10.00	248.00	0.15	0.47	38.90	0.60	38.50	1.00	1.40	223.00	0.04	549.00	4.07	119.50	2880.00	323.00	-0.01	107.50	23.80	49.30	0.01	1.37	2.90	1.40		
LE-16-09	93.51	94.76	730815	DUPLICATE	-0.01	5.86	12.60	-10.00	193.00	0.15	0.52	35.50	0.62	35.50	0.95	1.70	245.00	0.04	828.00	3.64	118.00	3500.00	303.00	-0.01	103.50	25.00	48.90	0.01	1.40	3.60	1.40		
LE-16-09	94.75	95.70	730816		-0.01	6.78	19.10	-10.00	231.00	0.15	0.50	36.00	0.52	35.60	0.52	1.00	264.00	0.05	678.00	5.71	198.00	2670.00	147.50	0.01	47.90	19.80	>100.00	0.01	0.74	1.90	3.40	203.00	
LE-16-10	15.05	16.35	730817		0.05	3.90	7.10	30.00	1.34	0.36	2.98	4.36	5.98	10.55	0.12	3.10	207.00	1.05	863.00	1.16	2.30	700.00	15.30	0.23	2.80	82.30	0.30	0.51	0.09	0.60	14.10		
LE-16-10	19.20	20.70	730818		0.02	2.86	4.40	10.00	33.40	0.05	0.65	103.50	1.11	11.95	0.24	-0.50	143.50	0.17	268.00	1.43	28.20	450.00	128.50	-0.01	20.40	25.40	32.90	0.07	0.84	0.30	1.30		
LE-16-10	20.70	21.60	730819		0.01	5.03	14.60	20.00	37.60	0.10	1.47	140.50	2.63	25.20	0.40	1.80	266.00	0.50	939.00	2.03	83.60	4040.00	197.00	-0.01	61.80	30.50	88.50	0.17	1.26	0.80	6.50		
LE-16-10	40.20	41.55	730820		0.08	6.72	27.80	40.00	129.00	0.69	1.66	218.00	3.78	26.70	0.88	1.60	620.00	0.83	2070.00	3.53	60.80	4910.00	439.00	0.42	46.90	28.20	39.20	0.21	2.75	1.50	7.70		
LE-16-10	41.55	42.90	730821		0.34	7.56	35.30	50.00	16.15	0.66	7.29	147.00	7.94	17.45	0.70	3.20	820.00	4.88	1650.00	1.29	7.60	1560.00	355.00	0.05	40.80	118.50	5.67	0.41	2.21	4.00	13.50		
LE-16-10	42.90	44.40	730822		0.04	5.77	22.90	10.00	215.00	0.27	0.49	42.90	1.12	34.90	1.31	-0.50	1090.00	0.11	2530.00	2.77	124.50	6710.00	401.00	-0.01	122.00	19.90	37.10	0.02	1.70	3.50	0.70		
LE-16-10	44.40	45.80	730823		0.02	6.57	25.20	-10.00	292.00	0.20	0.30	45.50	0.72	38.70	1.10	-0.50	660.00	0.06	1140.00	3.75	144.00	3290.00	363.00	-0.01	127.50	14.10	50.00	0.01	1.50	3.20	0.40		
LE-16-10	45.80	47.10	730824		0.06	6.93	27.10	-10.00	327.00	0.12	0.32	43.80	0.62	35.10	0.74	-0.50	760.00	0.05	1400.00														

LE-16-11	44.80	45.80	730858	0.01	8.48	3.70	20.00	191.00	0.05	0.69	42.60	1.00	56.50	2.85	2.10	600.00	0.11	1540.00	3.66	70.90	4920.00	780.00	-0.01	188.50	47.50	20.30	0.02	3.55	3.70	1.00	
LE-16-11	45.80	46.80	730859	0.03	7.56	9.20	10.00	269.00	0.04	0.62	18.00	0.87	34.40	0.54	6.90	262.00	0.08	1420.00	5.59	66.60	3090.00	154.00	0.01	45.90	35.70	46.80	0.01	0.67	1.40	1.40	
LE-16-12	14.45	15.00	730860	0.01	8.26	17.30	10.00	206.00	0.06	0.58	34.50	0.58	32.60	0.22	0.70	348.00	0.05	571.00	6.92	131.00	2440.00	44.00	0.01	8.50	36.70	>100.00	0.02	0.28	1.40	1.10	169.50
LE-16-12	15.00	16.50	730861	0.03	7.39	7.20	10.00	345.00	0.12	0.32	52.90	0.71	43.70	0.74	-0.50	6480.00	0.04	1160.00	3.29	109.50	2630.00	236.00	-0.01	79.50	13.50	61.70	0.01	0.97	2.40	0.80	
LE-16-12	16.50	17.50	730862	0.02	7.20	7.30	10.00	262.00	0.08	0.43	50.40	1.08	51.30	1.30	-0.50	4530.00	0.07	1890.00	2.69	85.40	5070.00	403.00	-0.01	149.50	23.80	23.60	0.02	1.76	3.50	0.50	
LE-16-12	17.50	19.00	730863	0.05	5.64	9.40	10.00	292.00	0.19	0.55	40.90	0.82	36.90	1.08	0.70	550.00	0.06	1280.00	2.68	86.90	4290.00	348.00	0.01	116.00	35.50	21.70	0.01	1.51	3.40	0.80	
LE-16-12	19.00	20.50	730864	-0.01	7.78	11.90	-10.00	260.00	0.11	0.36	32.80	0.62	39.00	0.90	-0.50	530.00	0.04	1000.00	5.26	147.00	3150.00	256.00	-0.01	91.00	27.20	70.60	0.01	1.04	2.50	0.40	
LE-16-12	20.50	22.00	730865	0.04	6.09	10.60	-10.00	161.00	0.09	0.38	31.00	0.83	34.30	0.94	-0.50	810.00	0.06	1730.00	3.46	110.00	4620.00	284.00	0.01	98.50	32.90	43.90	0.01	1.12	2.60	0.20	
LE-16-12	22.00	23.50	730866	0.02	7.27	26.30	-10.00	204.00	0.42	0.31	35.50	0.48	36.40	0.72	-0.50	520.00	0.03	704.00	5.34	109.00	1760.00	201.00	-0.01	70.50	14.60	45.00	0.01	0.89	1.90	0.70	
LE-16-12	22.01	23.51	730867	0.07	8.56	1.10	560.00	1.11	0.13	4.67	0.84	4.40	16.40	1.21	13.40	13.70	1.66	1030.00	2.52	3.40	740.00	23.90	-0.01	1.10	505.00	0.37	0.30	0.15	9.00	27.30	
LE-16-12	23.50	24.50	730868	0.04	7.47	10.30	-10.00	207.00	0.09	0.24	36.20	0.45	39.20	0.70	-0.50	740.00	0.02	721.00	5.75	82.00	1270.00	187.50	-0.01	67.00	14.50	36.60	0.01	0.80	1.40	0.40	
LE-16-12	24.50	26.00	730869	0.07	6.93	12.90	-10.00	209.00	0.08	0.28	33.50	0.58	40.00	0.64	-0.50	5430.00	0.04	824.00	3.58	110.50	2150.00	208.00	-0.01	78.60	13.00	48.30	0.01	0.87	2.00	0.70	
LE-16-12	26.00	27.50	730870	0.14	6.41	15.60	10.00	309.00	0.09	0.31	49.30	0.87	38.10	1.31	-0.50	5800.00	0.07	1640.00	2.22	70.50	4430.00	362.00	-0.01	81.50	14.10	21.30	0.01	1.75	2.70	1.00	
LE-16-12	27.50	29.00	730871	0.14	5.58	14.00	20.00	295.00	0.19	0.36	69.40	0.84	37.90	1.51	-0.50	3260.00	0.08	1380.00	1.71	68.60	4090.00	440.00	-0.01	110.00	15.90	13.05	0.02	2.07	3.90	1.00	
LE-16-12	29.00	30.50	730872	0.02	7.10	9.00	-10.00	284.00	0.12	0.24	65.20	0.71	43.60	0.53	-0.50	9510.00	0.04	731.00	2.46	86.30	1620.00	178.00	-0.01	97.90	15.70	31.40	0.01	0.79	1.80	0.40	
LE-16-12	30.50	32.00	730873	0.07	7.72	24.10	10.00	187.00	0.12	0.24	55.00	0.57	42.10	0.43	-0.50	8570.00	0.03	563.00	3.60	116.50	1370.00	144.50	-0.01	96.50	18.50	55.10	0.01	0.65	1.80	0.30	
LE-16-12	32.00	32.90	730874	-0.01	7.80	31.80	10.00	184.00	0.05	0.29	44.80	0.61	39.00	0.14	-0.50	7590.00	0.03	976.00	4.34	160.00	980.00	43.90	-0.01	65.40	93.40	>100.00	-0.01	0.22	1.50	0.70	159.00
LE-16-12	55.50	56.50	730875	-0.01	5.94	37.90	10.00	254.00	0.09	0.69	37.60	0.84	39.60	1.22	1.30	570.00	0.13	883.00	2.77	53.60	4630.00	440.00	0.03	128.00	42.80	11.45	0.02	1.79	3.60	1.00	
LE-16-12	56.50	57.80	730876	0.01	6.23	20.00	20.00	173.50	0.04	0.48	49.10	1.12	49.50	1.36	0.70	428.00	0.23	1220.00	2.36	100.00	2090.00	480.00	0.01	169.50	28.60	34.90	0.04	1.98	5.10	1.20	
LE-16-12	59.80	61.00	730877	0.01	6.03	41.00	20.00	113.50	0.09	0.89	165.00	1.41	51.80	1.88	1.80	570.00	0.82	659.00	1.68	83.60	4010.00	730.00	0.01	207.00	37.40	24.60	0.05	3.36	5.20	2.00	
LE-16-12	59.81	61.01	730878	0.01	5.92	33.70	20.00	99.50	0.09	0.83	46.70	0.88	52.00	1.58	1.20	430.00	0.21	572.00	1.99	84.60	3950.00	550.00	0.01	198.50	36.30	13.10	0.04	2.21	5.00	2.00	
LE-16-12	61.00	62.50	730879	0.02	6.18	26.50	10.00	149.50	0.06	0.48	29.20	0.82	38.40	1.03	0.50	620.00	0.14	1340.00	3.22	57.60	3540.00	326.00	0.01	129.00	47.50	26.60	0.02	1.34	3.60	0.60	
LE-16-12	85.00	86.50	730880	0.04	6.25	5.70	60.00	181.50	0.10	1.28	105.00	1.27	39.00	1.85	1.00	770.00	0.61	951.00	1.87	62.40	4310.00	630.00	-0.01	137.00	116.00	37.70	0.05	3.12	2.60	2.40	
LE-16-12	86.50	88.00	730881	0.01	8.14	6.30	40.00	55.80	0.10	0.17	112.50	0.44	34.40	5.19	2.40	185.00	0.06	170.00	2.89	39.10	1100.00	1430.00	-0.01	79.00	28.10	18.40	0.01	7.95	1.70	0.30	
LE-16-12	88.00	89.50	730882	-0.01	7.72	8.20	20.00	165.50	0.04	0.47	46.60	0.61	35.60	2.69	16.90	359.00	0.08	635.00	4.29	86.20	3010.00	670.00	-0.01	60.60	31.30	59.80	0.01	3.71	2.60	2.10	
LE-16-12	89.50	91.00	730883	0.03	7.78	7.00	20.00	269.00	0.04	0.49	34.90	0.60	36.70	1.58	3.70	2050.00	0.10	1000.00	4.37	88.10	3340.00	399.00	0.01	55.40	18.50	87.00	0.01	2.12	1.90	1.90	114.50
LE-16-12	91.00	92.40	730884	-0.01	7.93	7.40	10.00	343.00	0.02	0.41	37.80	0.63	42.60	0.84	6.90	2060.00	0.09	944.00	4.89	130.00	2650.00	273.00	0.01	75.10	24.30	100.00	0.01	1.25	2.30	1.40	
LE-16-13	5.50	7.00	730885	0.07	7.18	18.70	10.00	210.00	0.09	0.35	103.00	0.89	36.00	0.64	0.70	2780.00	0.12	504.00	4.69	104.00	1610.00	249.00	0.01	74.80	20.10	94.00	0.04	1.32	1.90	1.50	
LE-16-13	7.00	8.50	730886	0.04	7.03	22.90	-10.00	219.00	0.12	0.20	43.00	0.93	43.00	0.48	-0.50	9900.00	0.02	856.00	2.89	86.10	1310.00	159.00	-0.01	77.70	9.20	39.80	0.01	0.82	1.50	0.50	
LE-16-13	8.50	10.00	730887	0.04	5.72	18.10	-10.00	212.00	0.23	0.18	44.20	0.81	34.80	0.44	-0.50	8990.00	0.03	812.00	1.51	99.70	1110.00	165.00	-0.01	58.40	6.80	39.20	0.01	0.77	1.70	0.50	
LE-16-13	10.00	11.50	730888	0.02	8.01	17.80	-10.00	64.30	0.19	0.10	46.90	1.01	59.60	0.97	-0.50	>10000.00	0.04	765.00	1.25	54.90	640.00	380.00	-0.01	117.50	5.00	18.15	0.02	1.86	2.10	0.10	1.46
LE-16-13	10.01	11.51	730889	0.09	8.40	1.30	580.00	0.98	0.12	4.81	0.85	4.61	15.75	1.22	12.60	27.50	1.68	1080.00	2.58	3.20	770.00	19.00	-0.01	1.00	511.00	0.29	0.31	0.16	8.10	24.60	
LE-16-13	11.50	13.00	730890	0.04	7.84	21.10	-10.00	137.50	1.70	0.12	72.20	0.97	53.20	0.88	-0.50	>10000.00	0.03	685.00	2.11	65.90	770.00	374.00	-0.01	132.00	7.70	39.30	0.01	1.83	1.80	0.20	1.15
LE-16-13	13.00	14.50	730891	0.02	7.57	23.50	-10.00	63.50	0.23	0.10	39.60	0.72	47.00	0.44	-0.50	>10000.00	0.02	625.00	2.00	34.10	620.00	183.00	-0.01	113.50	5.20	23.60	0.01	0.93	0.90	0.10	1.35
LE-16-13	14.50	16.00	730892	0.01	7.44	25.60	-10.00	186.00	0.32	0.13	60.40	0.86	48.70	0.57	-0.50	>10000.00	0.03	898.00	2.23	42.10	1320.00	202.00	-0.01	61.20	7.20	18.75	0.01	1.13	1.20	0.10	1.29
LE-16-13	16.00	17.50	730893	0.03	6.65	29.90	-10.00	177.00	0.36	0.19	47.20	1.08	42.40	0.41	-0.50	>10000.00	0.03	868.00	1.68	50.70	1440.00	162.00	-0.01	69.50	6.50	19.80	0.01	0.82	1.10	0.50	1.16
LE-16-13	17.50	19.00	730894	0.02	7.73	39.10	-10.00	257.00	0.31	0.20	58.00	0.79	49.30	0.51	-0.50	>10000.00	0.03	864.00	2.84	80.90	1200.00	181.00	-0.01	61.00	9.60	33.20	0.01	0.96	1.40	0.50	1.10
LE-16-13	19.00	20.50	730895	0.02	7.33	10.50	-10.00	294.00	0.22	0.13	55.50	0.85	47.90	0.27	-0.50	>10000.00	0.02	830.00	2.13	167.50	1190.00	86.60	-0.01	92.80	6.90	84.80	0.01	0.49	1.60	0.10	1.42
LE-16-13	20.50	22.00	730896	0.01	8.11	15.30	-10.00	112.50	0.34	0.08	40.80	1.12	54.70	0.37	-0.50	>10000.00	0.03	674.00	1.35	46.90	400.00	125.50	-0.01	71.60	4.00	21.50	0.01	0.73	0.80	0.10	1.79
LE-16-13	22.00	23.50	730897</																												

LE-16-14	42.01	43.51	730930	BLANK	0.07	8.33	1.00	570.00	1.35	0.11	4.75	0.80	4.48	17.15	1.19	12.00	54.10	1.62	1060.00	2.56	3.40	770.00	17.70	-0.01	1.10	517.00	0.80	0.31	0.17	9.00	25.50	
LE-16-14	43.50	45.00	730931		-0.01	8.21	17.80	-10.00	163.50	0.04	0.08	36.20	0.87	59.00	0.48	-0.50	>10000.00	0.03	744.00	1.49	54.10	500.00	187.00	-0.01	91.20	4.70	46.90	0.01	0.88	1.30	0.10	1.54
LE-16-14	45.00	46.50	730932		0.01	8.08	12.90	-10.00	54.20	0.06	0.07	19.00	0.72	54.40	0.24	-0.50	>10000.00	0.02	682.00	1.03	46.50	610.00	91.90	-0.01	143.00	3.70	35.80	0.01	0.42	0.70	0.10	1.77
LE-16-14	46.50	48.00	730933		0.01	8.27	22.10	-10.00	180.00	0.33	0.11	46.40	1.18	59.30	0.66	-0.50	>10000.00	0.03	1100.00	1.34	78.10	1510.00	252.00	-0.01	113.50	5.00	42.50	0.01	1.23	1.60	0.40	1.73
LE-16-14	48.00	49.50	730934		0.01	7.53	16.30	-10.00	233.00	0.05	0.22	23.90	0.30	34.80	0.27	0.80	2430.00	0.02	278.00	6.15	152.00	1120.00	42.20	-0.01	36.90	12.90	>100.00	-0.01	0.21	1.50	1.10	336.00
LE-16-14	49.50	51.00	730935		0.03	6.98	14.50	-10.00	137.50	0.04	0.22	15.75	0.63	34.90	0.14	0.80	5810.00	0.03	1360.00	4.26	64.00	590.00	18.00	-0.01	47.00	11.30	>100.00	0.01	0.10	1.00	1.60	149.50
LE-16-14	51.00	52.00	730936		0.01	7.34	6.80	-10.00	236.00	0.03	0.31	22.00	0.34	31.70	0.15	0.80	80.00	0.01	159.00	6.68	100.50	1200.00	21.20	-0.01	15.60	16.70	>100.00	-0.01	0.10	1.20	2.90	213.00
LE-16-16	42.70	43.50	730937		0.05	5.93	17.30	50.00	41.80	2.94	0.28	16.55	0.52	21.30	2.04	0.60	24.90	0.02	806.00	4.23	14.00	1180.00	312.00	0.01	2.10	7.60	9.00	-0.01	1.79	0.30	2.90	
LE-16-16	43.50	45.00	730938		0.06	6.06	13.50	10.00	29.30	7.41	0.17	20.30	0.52	23.40	2.45	0.90	25.40	0.02	751.00	4.26	9.20	1110.00	378.00	-0.01	4.50	3.70	5.18	-0.01	2.07	0.40	2.70	
LE-16-16	45.00	46.50	730939		0.04	6.29	9.90	10.00	55.80	5.92	0.15	23.20	0.50	24.10	2.61	-0.50	36.10	0.02	788.00	3.86	14.20	1110.00	417.00	-0.01	10.20	3.90	3.58	-0.01	2.20	0.60	1.90	
LE-16-16	45.01	46.51	730940	DUPLICATE	0.05	6.41	6.30	10.00	57.50	8.53	0.14	27.00	0.52	25.70	2.81	0.50	37.40	0.02	701.00	3.90	13.30	1090.00	460.00	-0.01	9.70	4.40	3.06	-0.01	2.62	0.60	1.90	
LE-16-16	46.50	48.00	730941		0.09	6.93	9.50	20.00	51.10	14.20	0.15	34.00	0.48	32.00	3.68	-0.50	53.30	0.03	313.00	3.17	29.30	1130.00	620.00	-0.01	28.40	6.60	6.11	0.01	3.34	1.50	1.30	
LE-16-16	48.00	49.50	730942		0.04	6.74	5.20	10.00	48.80	4.25	0.14	30.60	0.61	28.70	3.51	0.60	37.80	0.03	796.00	3.86	22.70	1140.00	560.00	-0.01	11.00	5.30	7.65	-0.01	3.01	0.70	2.00	
LE-16-16	49.50	51.00	730943		0.07	6.37	4.20	30.00	78.30	13.30	0.22	23.20	0.47	24.30	2.61	0.50	26.00	0.03	625.00	4.38	18.10	1060.00	396.00	0.01	2.10	8.10	7.58	-0.01	2.24	0.30	2.30	
LE-16-16	51.00	52.50	730944		0.03	7.06	42.30	50.00	87.40	2.09	0.17	42.90	0.33	23.50	4.80	-0.50	27.20	0.02	142.00	3.30	19.60	860.00	740.00	0.01	1.70	14.10	11.05	-0.01	4.14	0.30	0.60	
LE-16-16	52.50	53.30	730945		0.08	6.36	23.00	40.00	25.40	4.12	0.39	25.80	0.43	23.60	2.62	-0.50	30.50	0.03	221.00	4.34	20.20	1030.00	388.00	0.01	2.40	22.40	9.04	0.01	2.08	0.50	0.90	

APPENDIX 2. JORC Code (2012) Table 1 Report: Reverse Circulation Drilling, Lemare Spodumene Project, Quebec, Canada, October 2016.

Section 1: Sampling Techniques and Data

Criteria	JORC Code explanation	Commentary
Sampling techniques	<i>Nature and quality of sampling (eg cut channels, random chips, or specific specialised industry standard measurement tools appropriate to the minerals under investigation, such as down hole gamma sondes, or handheld XRF instruments, etc). These examples should not be taken as limiting the broad meaning of sampling.</i>	Diamond drilling was used to collect NQ core. This core was split in half to provide half core sample which was sent to ALS Minerals Laboratory in Val d'Or, Quebec, Canada for analysis. Selected intervals were sampled to geological contacts or 1.5m intervals, maximum sample was 1.95m and minimum sample was 0.25m.
	<i>Include reference to measures taken to ensure sample representativeness and the appropriate calibration of any measurement tools or systems used.</i>	Core was split down the middle producing equal halves with one half being sampled while the other is stored in core trays for preservation.
	<i>Aspects of the determination of mineralisation that are Material to the Public Report.</i>	Samples were sent to ALS Minerals laboratories in Val d'Or, Quebec, Canada and analysed for multi elements by 4 acid digest ICP-MS method ME-MS61, overlimit for Ta using Lithium Borate Fusion ICP-MS method ME-MS85, overlimit for Li using ore grade 4 acid digest ICP-AES method Li-OG63.
	<i>In cases where 'industry standard' work has been done this would be relatively simple (eg 'reverse circulation drilling was used to obtain 1 m samples from which 3 kg was pulverised to produce a 30 g charge for fire assay'). In other cases more explanation may be required, such as where there is coarse gold that has inherent sampling problems. Unusual commodities or mineralisation types (eg submarine nodules) may warrant disclosure of detailed information.</i>	The drilling program is reconnaissance in nature with holes sited to test coincident geological and geochemical anomaly.
Drilling techniques	<i>Drill type (eg core, reverse circulation, open-hole hammer, rotary air blast, auger, Bangka, sonic, etc) and details (eg core diameter, triple or standard tube, depth of diamond tails, face-sampling bit or other type, whether core is oriented and if so, by what method, etc).</i>	All holes were completed by G4 Nemaska Drilling with NQ diamond coring at angles between -43 and -70 degrees with a maximum depth of 284.3m.
Drill sample recovery	<i>Method of recording and assessing core and chip sample recoveries and results assessed.</i>	Overall recoveries were >95% with no significant core loss. Diamond core was reconstructed into continuous runs and measured lengths checked against core block depths.
	<i>Measures taken to maximise sample recovery and ensure representative nature of the samples.</i>	
	<i>Whether a relationship exists between sample recovery and grade and whether sample bias may have occurred due to preferential loss/gain of fine/coarse material.</i>	Sample recovery was adequate for the drilling technique with no sample bias occurring.
Logging	<i>Whether core and chip samples have been geologically and geotechnically logged to a level of detail to support appropriate Mineral Resource estimation, mining studies and metallurgical studies.</i>	Diamond core was geologically logged throughout each entire hole by the geologist on site overseeing the drill program. Half core was sent to the laboratory while the remaining core was stored in core trays.
	<i>Whether logging is qualitative or quantitative in nature. Core (or costean, channel, etc) photography.</i>	Logging recorded abundance and type of minerals, veining, alteration, mineralisation, colour, weathering and rock types using a standardised logging system. Photos were taken of the entire core for each hole.
	<i>The total length and percentage of the relevant intersections logged.</i>	All holes were logged over their entire length.
Sub-sampling techniques and sample preparation	<i>If core, whether cut or sawn and whether quarter, half or all core taken.</i>	Core was split in half using a hydraulic core splitter with half sample being submitted to the laboratory for analysis.
	<i>If non-core, whether riffled, tube sampled, rotary split, etc and whether sampled wet or dry.</i>	
	<i>For all sample types, the nature, quality and appropriateness of the sample preparation technique.</i>	Samples were sent to ALS Minerals laboratories in Val d'Or, Quebec, Canada where the entire sample was crushed, >70% -2mm fraction, then pulverised to 85% passing 75 microns or better.

	<i>Quality control procedures adopted for all sub-sampling stages to maximise representativeness of samples.</i>	Half core is considered appropriate for representativeness of samples.
	<i>Measures taken to ensure that the sampling is representative of the in situ material collected, including for instance results for field duplicate/second-half sampling.</i>	Field duplicate samples (second core-half) and blanks were submitted approximately every 20 samples for each hole.
	<i>Whether sample sizes are appropriate to the grain size of the material being sampled.</i>	Spodumene mineralisation was fairly homogeneous through the sampled intervals with sample size being appropriate for the material.
<i>Quality of assay data and laboratory tests</i>	<i>The nature, quality and appropriateness of the assaying and laboratory procedures used and whether the technique is considered partial or total.</i>	Samples were sent to ALS Minerals laboratories in Val d'Or, Quebec, Canada and analysed for multi elements by 4 acid digest ICP-MS method ME-MS61, overlimit for Ta using Lithium Borate Fusion ICP-MS method ME-MS85, overlimit for Li using ore grade 4 acid digest ICP-AES method Li-OG63. These methods give a total analysis.
	<i>For geophysical tools, spectrometers, handheld XRF instruments, etc, the parameters used in determining the analysis including instrument make and model, reading times, calibrations factors applied and their derivation, etc.</i>	Not applicable, no instruments used.
	<i>Nature of quality control procedures adopted (eg standards, blanks, duplicates, external laboratory checks) and whether acceptable levels of accuracy (ie lack of bias) and precision have been established.</i>	Field duplicates (second-half core) and blanks were submitted approximately every 20 samples for each hole.
<i>Verification of sampling and assaying</i>	<i>The verification of significant intersections by either independent or alternative company personnel.</i>	A minimum of 2 company geologists have verified significant intersections.
	<i>The use of twinned holes.</i>	No twinned holes were drilled and are not considered necessary for this reconnaissance program.
	<i>Documentation of primary data, data entry procedures, data verification, data storage (physical and electronic) protocols.</i>	Drill hole data and geological logs were recorded on paper in the field then entered into digital format before being uploaded to the company SQL database.
	<i>Discuss any adjustment to assay data.</i>	Lithium values have been converted to Li ₂ O by converting Li ppm to % then multiplying by 2.153
<i>Location of data points</i>	<i>Accuracy and quality of surveys used to locate drill holes (collar and down-hole surveys), trenches, mine workings and other locations used in Mineral Resource estimation.</i>	Drill hole coordinates were determined using a hand held GPS. Each drill hole had downhole surveys approximately every 30m
	<i>Specification of the grid system used.</i>	UTM NAD83 zone 18
	<i>Quality and adequacy of topographic control.</i>	RL determined using hand held GPS
<i>Data spacing and distribution</i>	<i>Data spacing for reporting of Exploration Results.</i>	Holes were drilled on nominal 50m spaced sections.
	<i>Whether the data spacing and distribution is sufficient to establish the degree of geological and grade continuity appropriate for the Mineral Resource and Ore Reserve estimation procedure(s) and classifications applied.</i>	The drilling is reconnaissance in nature and not at a stage where a Mineral Resource estimation is appropriate.
	<i>Whether sample compositing has been applied.</i>	No sample compositing was applied.
<i>Orientation of data in relation to geological structure</i>	<i>Whether the orientation of sampling achieves unbiased sampling of possible structures and the extent to which this is known, considering the deposit type.</i>	The holes were drilled perpendicular to the mapped pegmatite. The drill orientation is considered appropriate for the deposit type.
	<i>If the relationship between the drilling orientation and the orientation of key mineralised structures is considered to have introduced a sampling bias, this should be assessed and reported if material.</i>	The holes were drilled perpendicular to mapped pegmatite and no sampling bias is considered to have been introduced.

Sample security	The measures taken to ensure sample security.	The samples were bagged and bulk-packaged securely and couriered to the laboratory in Val d'Or Canada.
Audits or reviews	The results of any audits or reviews of sampling techniques and data.	No bias or sampling issues were noted when reviewing QAQC data including field duplicates and blanks.

Section 2: Reporting of Exploration Results

Criteria	JORC Code explanation	Commentary
Mineral tenement and land tenure status	Type, reference name/number, location and ownership including agreements or material issues with third parties such as joint ventures, partnerships, overriding royalties, native title interests, historical sites, wilderness or national park and environmental settings.	The Lemare lithium project is located in the James Bay region of Quebec, Canada (Figure 1). The project is secured by an option agreement ("Lemare Option") entered into by the Company's wholly owned subsidiary Lepidico Ltd and the owner of Lemare, Critical Elements Corporation (TSX-V:CRE), on 11 February 2016. Full details were reported to the market on 12 February 2016.
	The security of the tenure held at the time of reporting along with any known impediments to obtaining a licence to operate in the area.	Tenure is secure with no known impediments.
Exploration done by other parties	Acknowledgment and appraisal of exploration by other parties.	Exploration was conducted by Consul-Teck contracting to Platypus Minerals Ltd.
Geology	Deposit type, geological setting and style of mineralisation.	Pegmatite hosted spodumene mineralisation in Archaean greenstone.
Drill hole Information	A summary of all information material to the understanding of the exploration results including a tabulation of the following information for all Material drill holes:	Refer to Appendix 1
	o easting and northing of the drill hole collar	Refer to Appendix 1
	o elevation or RL (Reduced Level – elevation above sea level in metres) of the drill hole collar	Refer to Appendix 1
	o dip and azimuth of the hole	Refer to Appendix 1
	o down hole length and interception depth	Refer to Appendix 1
	o hole length.	Refer to Appendix 1
	If the exclusion of this information is justified on the basis that the information is not Material and this exclusion does not detract from the understanding of the report, the Competent Person should clearly explain why this is the case.	N/A
Data aggregation methods	In reporting Exploration Results, weighting averaging techniques, maximum and/or minimum grade truncations (eg cutting of high grades) and cut-off grades are usually Material and should be stated.	Overall intersections were based on geological boundaries – ie full downhole width of pegmatite intrusions. Inclusive high grade zones calculated using 1% Li ₂ O cut with up to 1m of internal dilution.
	Where aggregate intercepts incorporate short lengths of high grade results and longer lengths of low grade results, the procedure used for such aggregation should be stated and some typical examples of such aggregations should be shown in detail.	
	The assumptions used for any reporting of metal equivalent values should be clearly stated.	Not applicable, no metal equivalent values are stated.

<i>Relationship between mineralisation widths and intercept lengths</i>	• <i>These relationships are particularly important in the reporting of Exploration Results.</i>	The pegmatite intrusives are sub vertical and true widths have been calculated and reported next to downhole intervals.
	• <i>If the geometry of the mineralisation with respect to the drill hole angle is known, its nature should be reported.</i>	Drilling is perpendicular to the strike of the pegmatites. Pegmatites dip sub vertically.
	• <i>If it is not known and only the down hole lengths are reported, there should be a clear statement to this effect (eg 'down hole length, true width not known').</i>	True widths have been calculated and reported next to downhole intervals.
<i>Diagrams</i>	• <i>Appropriate maps and sections (with scales) and tabulations of intercepts should be included for any significant discovery being reported. These should include, but not be limited to a plan view of drill hole collar locations and appropriate sectional views.</i>	A plan and various diagrams showing sample locations are provided in the body of the announcement.
<i>Balanced reporting</i>	• <i>Where comprehensive reporting of all Exploration Results is not practicable, representative reporting of both low and high grades and/or widths should be practiced to avoid misleading reporting of Exploration Results.</i>	Two cross sections are provided in the body of the report. A table of intercepts for all 16 holes is reported in Appendix 1
<i>Other substantive exploration data</i>	• <i>Other exploration data, if meaningful and material, should be reported including (but not limited to): geological observations; geophysical survey results; geochemical survey results; bulk samples – size and method of treatment; metallurgical test results; bulk density, groundwater, geotechnical and rock characteristics; potential deleterious or contaminating substances.</i>	Spodumene is the only lithium mineral observed and recorded in the drilling.
<i>Further work</i>	• <i>The nature and scale of planned further work (eg tests for lateral extensions or depth extensions or large-scale step-out drilling).</i>	Geological mapping and surface rock chip sampling have confirmed lateral extensions of spodumene bearing pegmatites approximately 300m to the SW. Further drilling is anticipated to test this extension.
	• <i>Diagrams clearly highlighting the areas of possible extensions, including the main geological interpretations and future drilling areas, provided this information is not commercially sensitive.</i>	Platypus Minerals Ltd is assessing all historical and current information to refine drilling targets.

The information in this report that relates to Exploration Results is based on information compiled by Mr Tom Dukovcic, who is an employee of the Company and a member of the Australian Institute of Geoscientists and who has sufficient experience relevant to the styles of mineralisation and the types of deposit under consideration, and to the activity that has been undertaken, to qualify as a Competent Person as defined in the 2012 edition of the "Australasian Code for Reporting of Exploration Results, Mineral Resources and Ore Reserves." Mr Dukovcic consents to the inclusion in this report of information compiled by him in the form and context in which it appears.
